

# Control of Magnetism with Oxide Hybrid Structures

**Siming Wang**

*University of California San Diego*

Magnetism



Oxide



FG03-87ER-45332

FA9550-12-1-0381

# Acknowledgement



Prof. Ivan K. Schuller  
Principal Investigator



Prof. Jose de la Venta  
Thin Film, Magnetism



Dr. Thomas Saerbeck  
Diffraction, Magnetism



Dr. Juan Gabriel Ramirez  
Thin Film, Magnetism (FMR)



Ilya Valmianski  
AFM, SEM, Fabrication  
ivalmian@ucsd.edu




Siming Wang  
Thin Film, Simulation,  
Fabrication

# Outline

- ***Introduction***
  - Review Control of Magnetism
  - Phase Transition in Vanadium Oxide ( $\text{VO}_x$ )
- ***Control of Magnetism with  $\text{VO}_x/\text{FM}$*** 
  - Tuning with Magnetostrictive Effect
- ***Coercivity Enhancement in  $\text{V}_2\text{O}_3/\text{Ni}$*** 
  - Competing Length Scales on Nanoscale
- ***Summary and Outlook***


# Control of Magnetism

## Heat Assisted Magnetic Recording (HAMR)

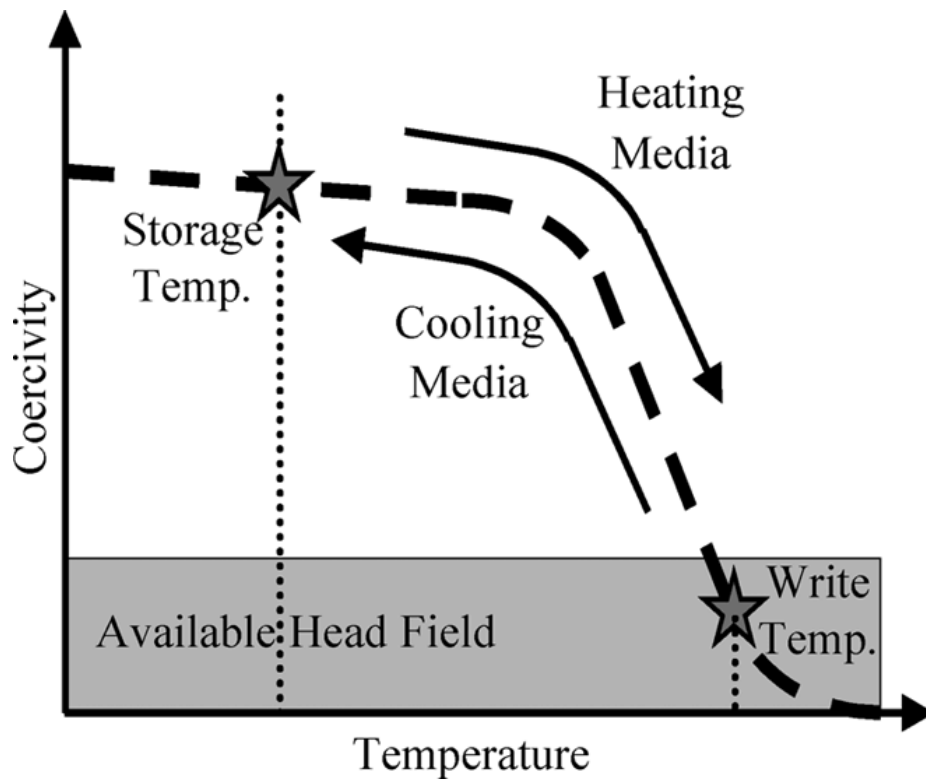

- Microwave Assisted
- Acoustic Phonon Assisted
- Ultrafast Laser Induced

# “Sun-Wheel” of Oxide Hybrid Structures

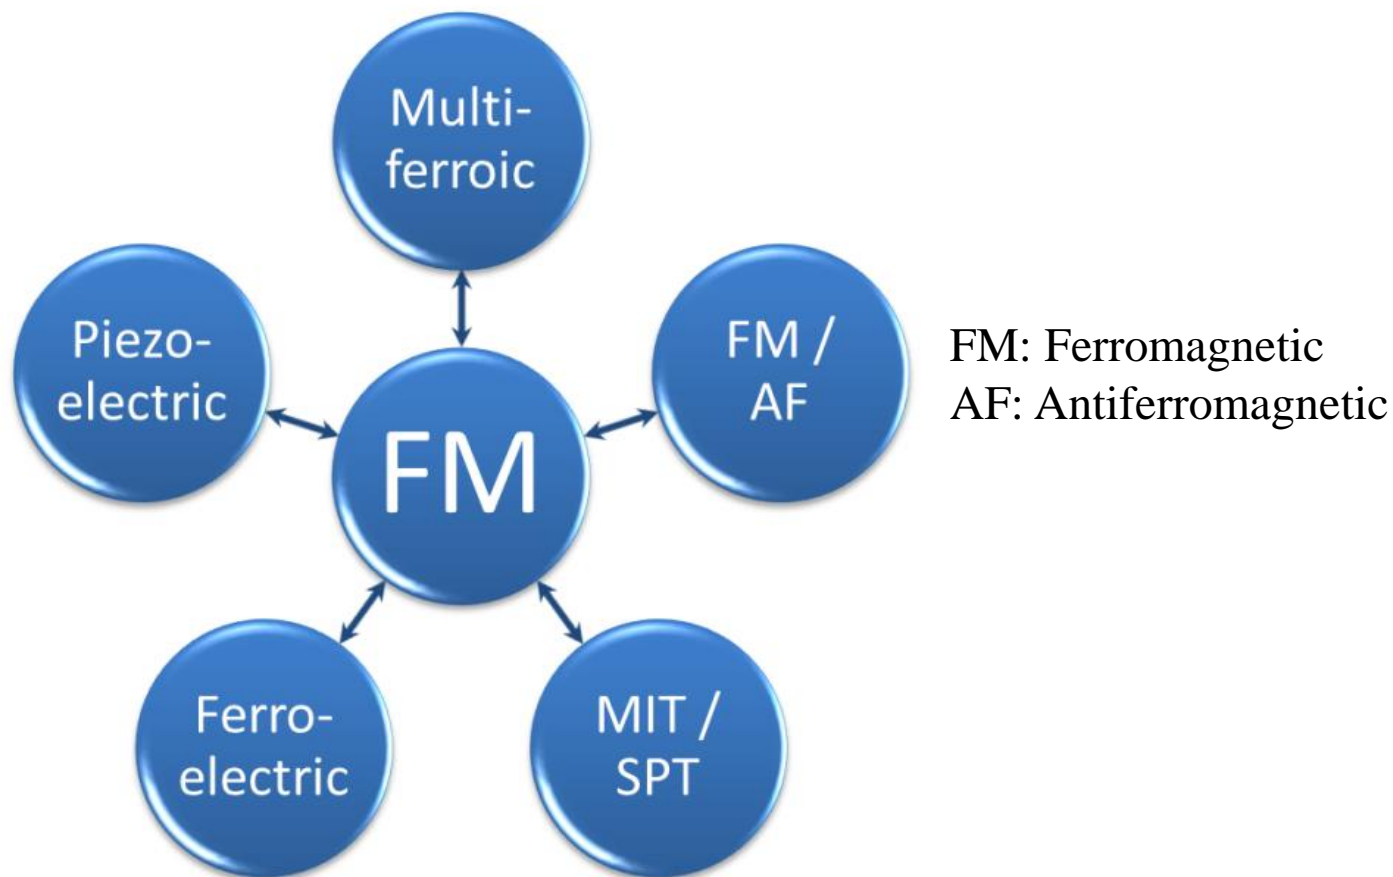


T. Saerbeck, J. de la Venta, S. Wang, J. G. Ramirez, M. Erekhinsky, I. Valmianski, I. K. Schuller, J. Mater. Res., Invited Review (2014)

MIT: Metal Insulator Transition  
SPT: Structural Phase Transition

# Control of Magnetism with SPT

BaTiO<sub>3</sub>/Fe Bilayer: Control through Interface Strain Coupling

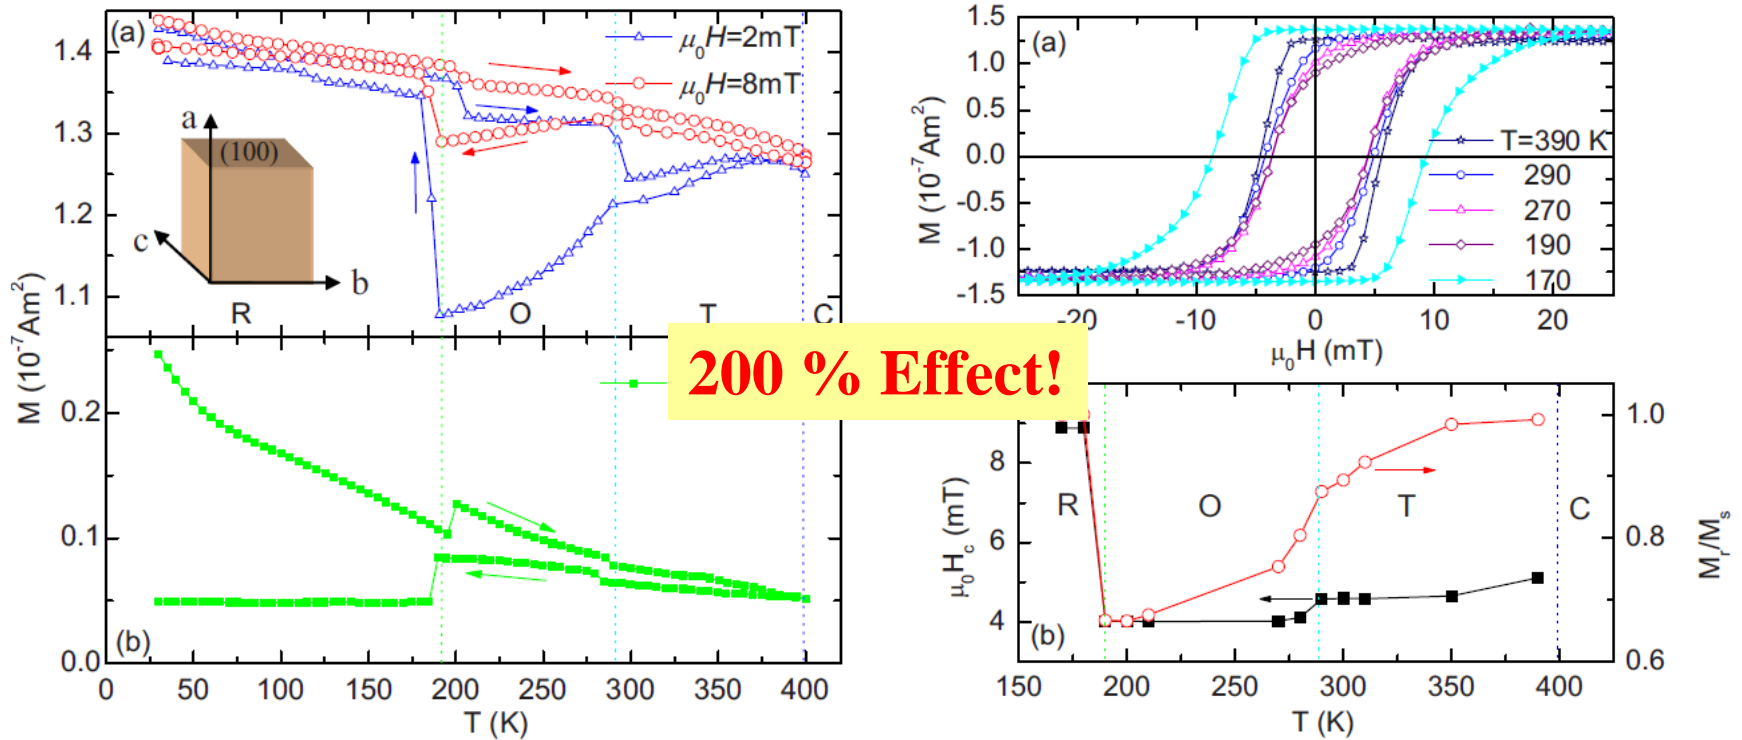

S. Sahoo *et al.*, Phys. Rev. B **76**, 092108 (2007)


# Phase Transition in $\text{VO}_2$

MIT


SPT

High-T Rutile

Low-T Monoclinic

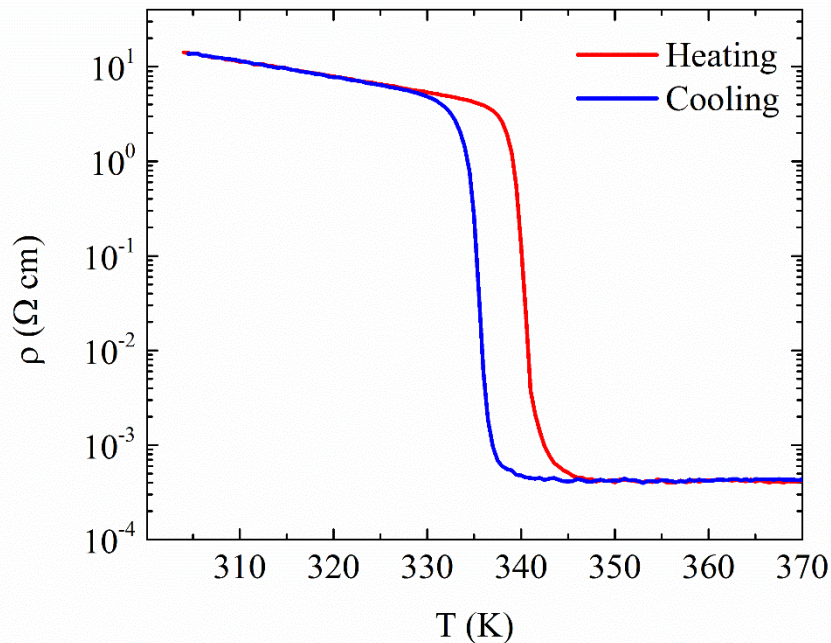

$$T_C = 340 \text{ K}$$

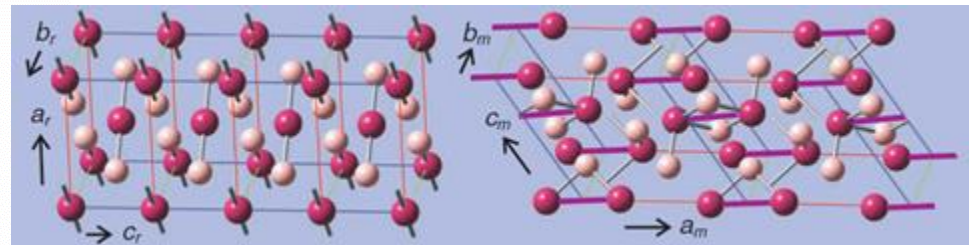

P. Baum *et al.*, Science **318**, 788 (2007)

$\sim 1\%$  Lattice Distortion


$\sim 1\%$  Volume Change



# Phase Transition in $V_2O_3$


MIT

SPT

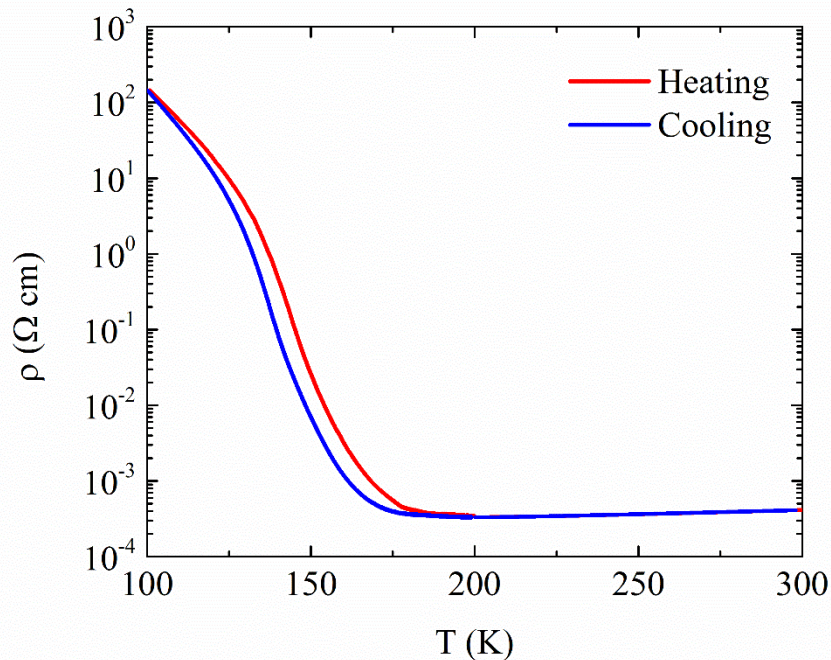

$T_C = 150 - 165$  K

High-T Rhombohedral Low-T Monoclinic

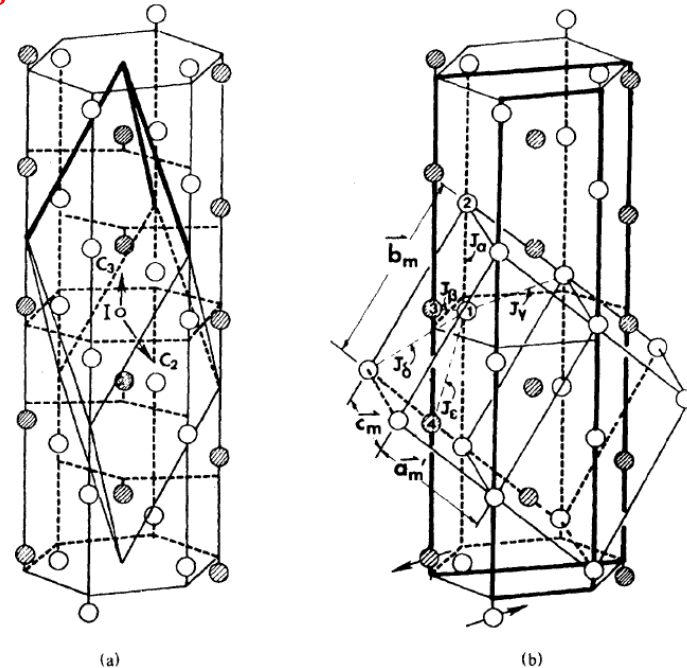

R. E. Word *et al.*, Phys. Rev. B **23**, 3533 (1981)

~ 1 % Lattice Distortion

~ 1 % Volume Change



# Why $\text{VO}_x$ ?

- First Order Phase Transition

**Abrupt** Structural Change in **Narrow** Temperature Range

- Choice of Transition Temperatures

$$T_C(\text{VO}_2) = 340 \text{ K}, T_C(\text{V}_2\text{O}_3) = 150 - 165 \text{ K}$$

- Multiple Driving Forces to Induce SPT

Temperature, Voltage/Current, Light, Gating, Pressure, etc.

# Outline

- *Introduction*

- Review Control of Magnetism
- Phase Transition in Vanadium Oxide ( $\text{VO}_x$ )

- *Control of Magnetism with  $\text{VO}_x/\text{FM}$*

- Tuning with Magnetostrictive Effect



- *Coercivity Enhancement in  $\text{V}_2\text{O}_3/\text{Ni}$*

- Competing Length Scale on Nanoscale

- *Conclusions*


# VO<sub>2</sub> / Ni

100 nm VO<sub>2</sub> / 10 nm Ni

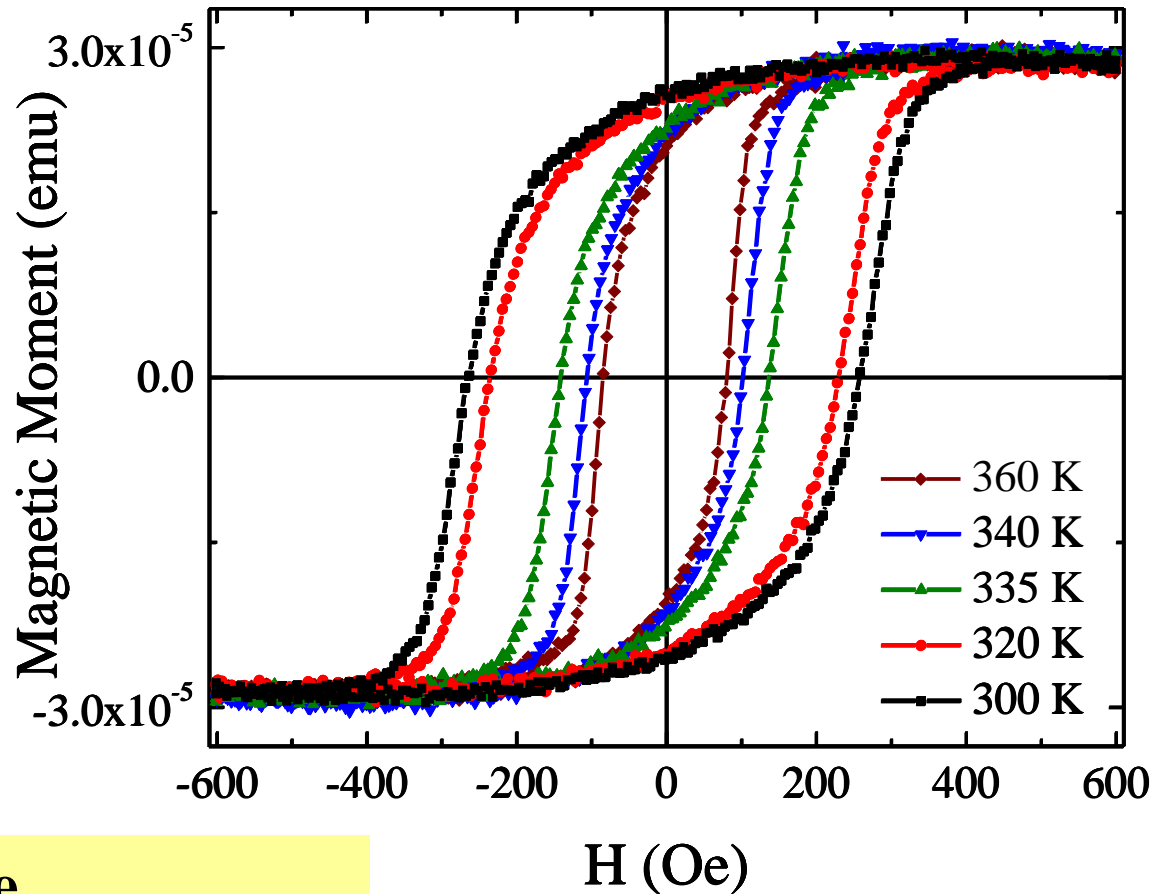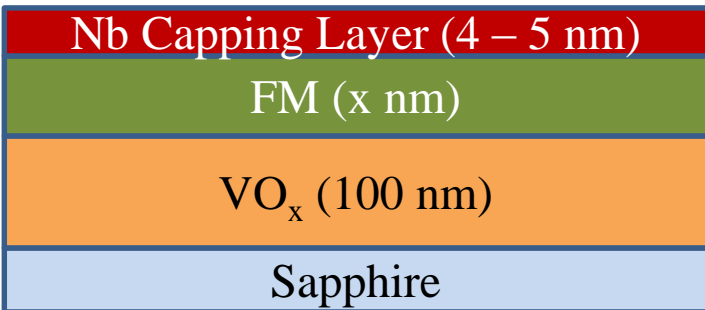


**200 % Coercivity Change**  
**across VO<sub>2</sub> Phase Transition at 340 K**

# Correlation: Phase Transition & Magnetism

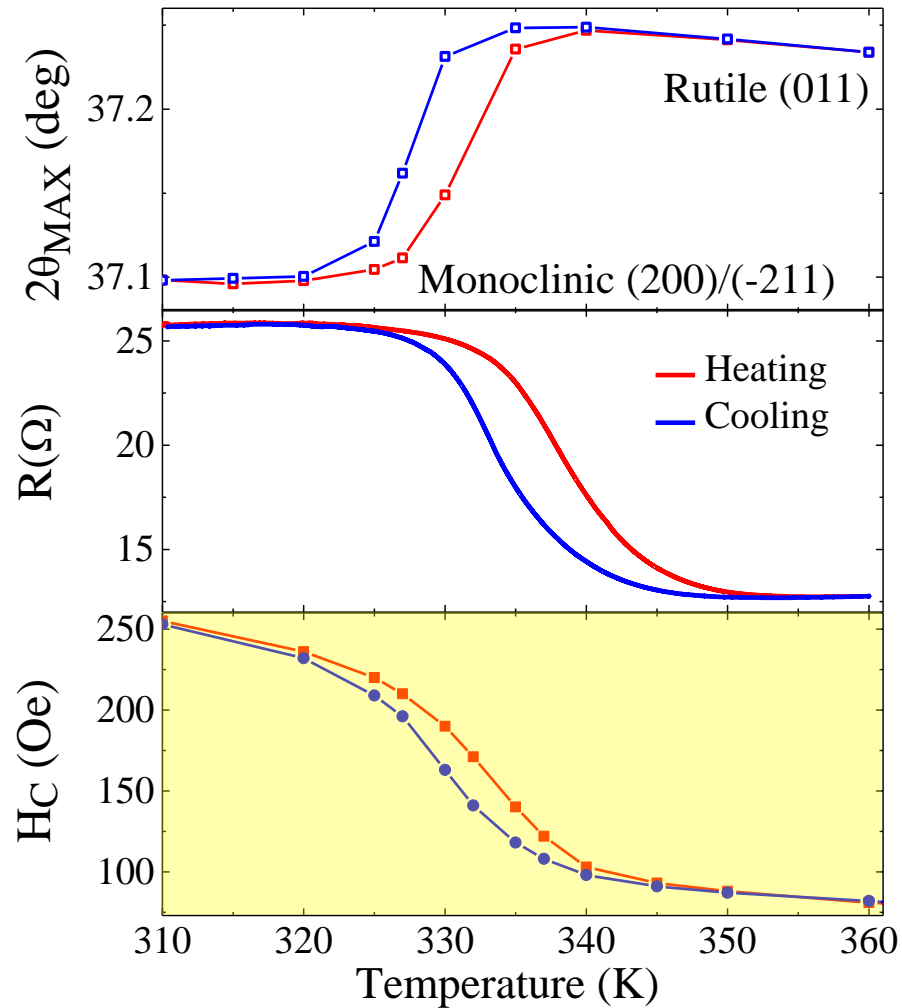

**Temperature Dependence & Thermal Hysteresis of  $H_C$  Coincide with MIT & SPT of  $VO_2$**

# Ni Thickness Dependence

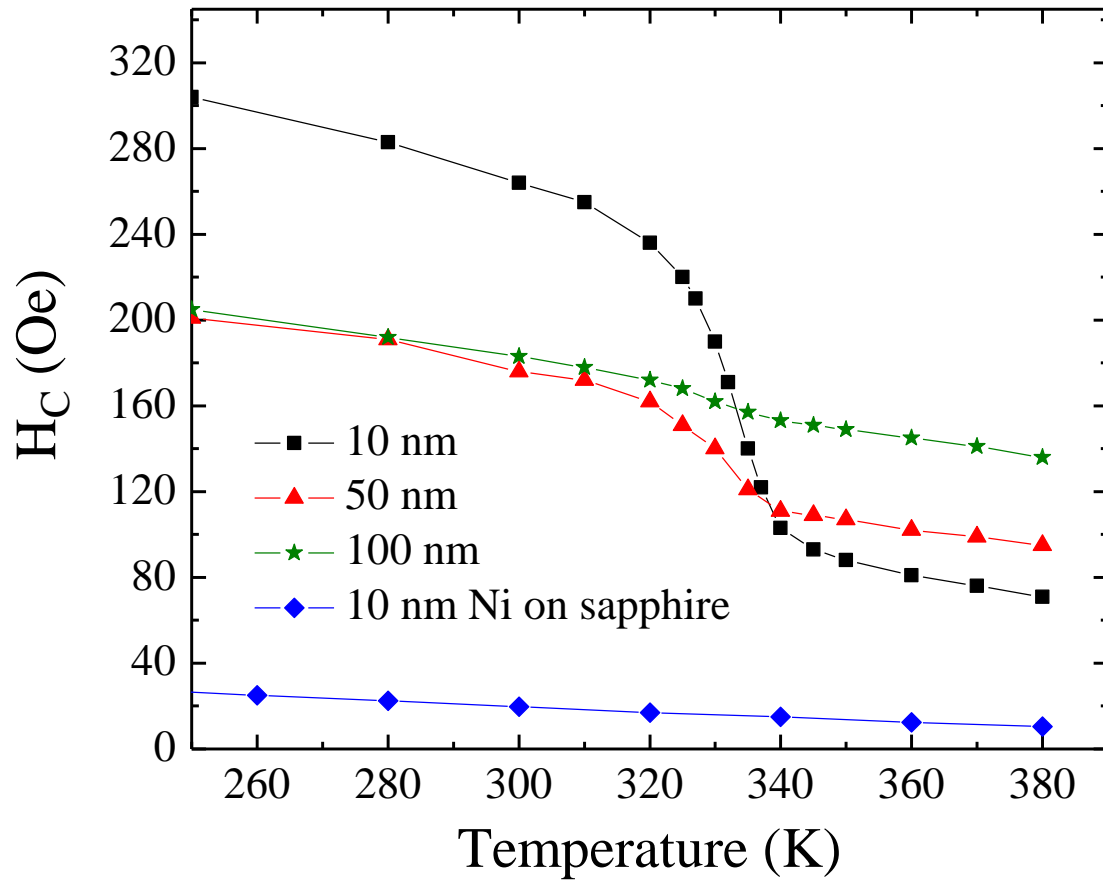

Effect **Reduces** as Ni Thickness **Increases**



**Interface Effect**


# Magnetostriction

Change of Dimensions in the Applied Field Direction

Magnetostriction Coefficient  $\lambda = \frac{\Delta L}{L}$


$\lambda < 0$  Contracts when Magnetized

$\lambda > 0$  Elongates when Magnetized

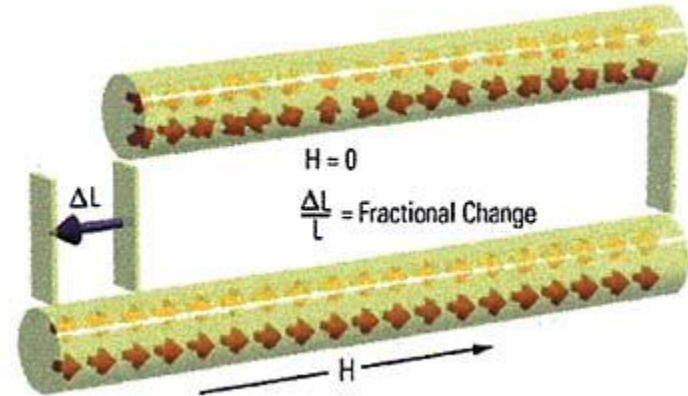

Polycrystalline Ni  $\lambda$


$(10^{-6})$

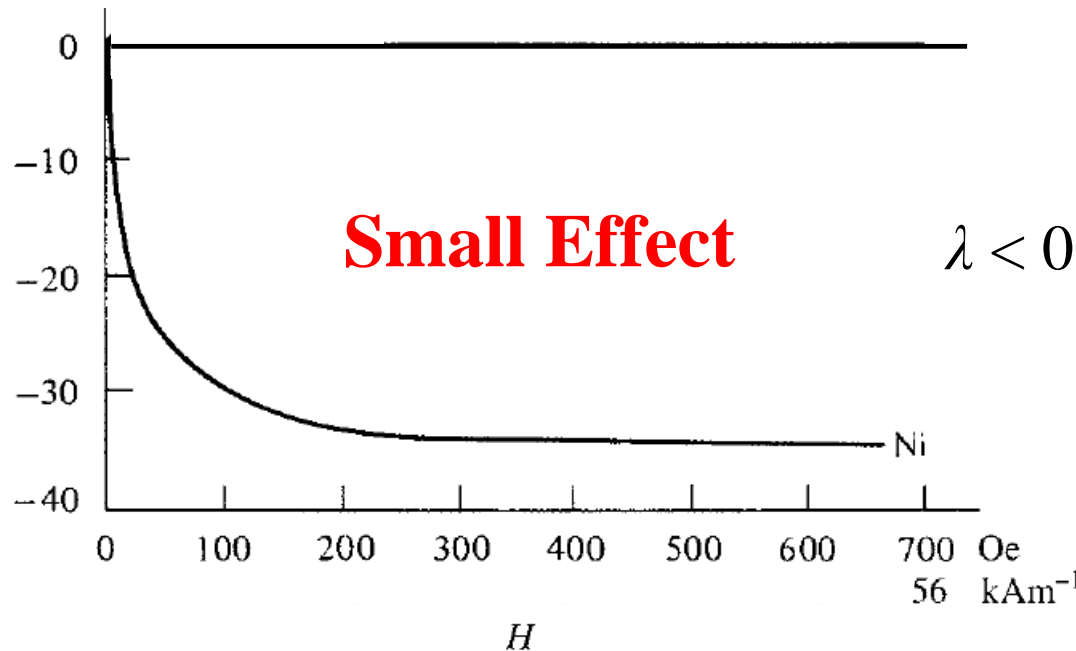




# Inverse Magnetostriction

Change of Magnetization due to Applied Stress

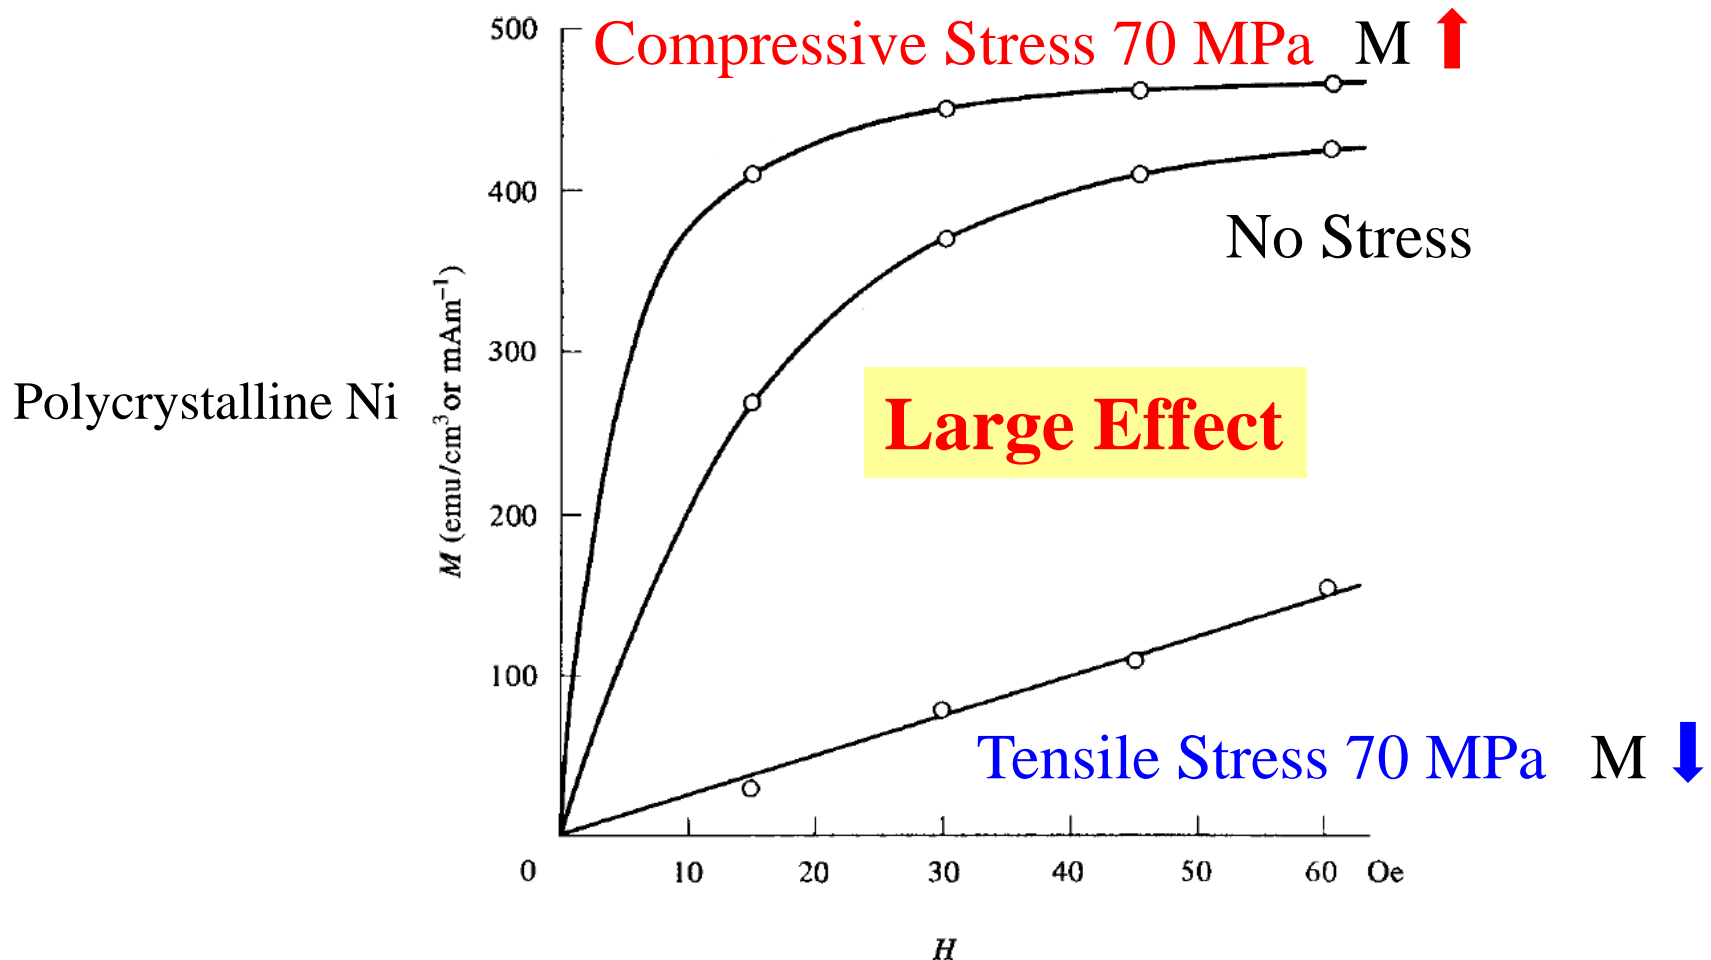

# Magnetization vs. Temperature


100 nm VO<sub>2</sub> / 10 nm Ni

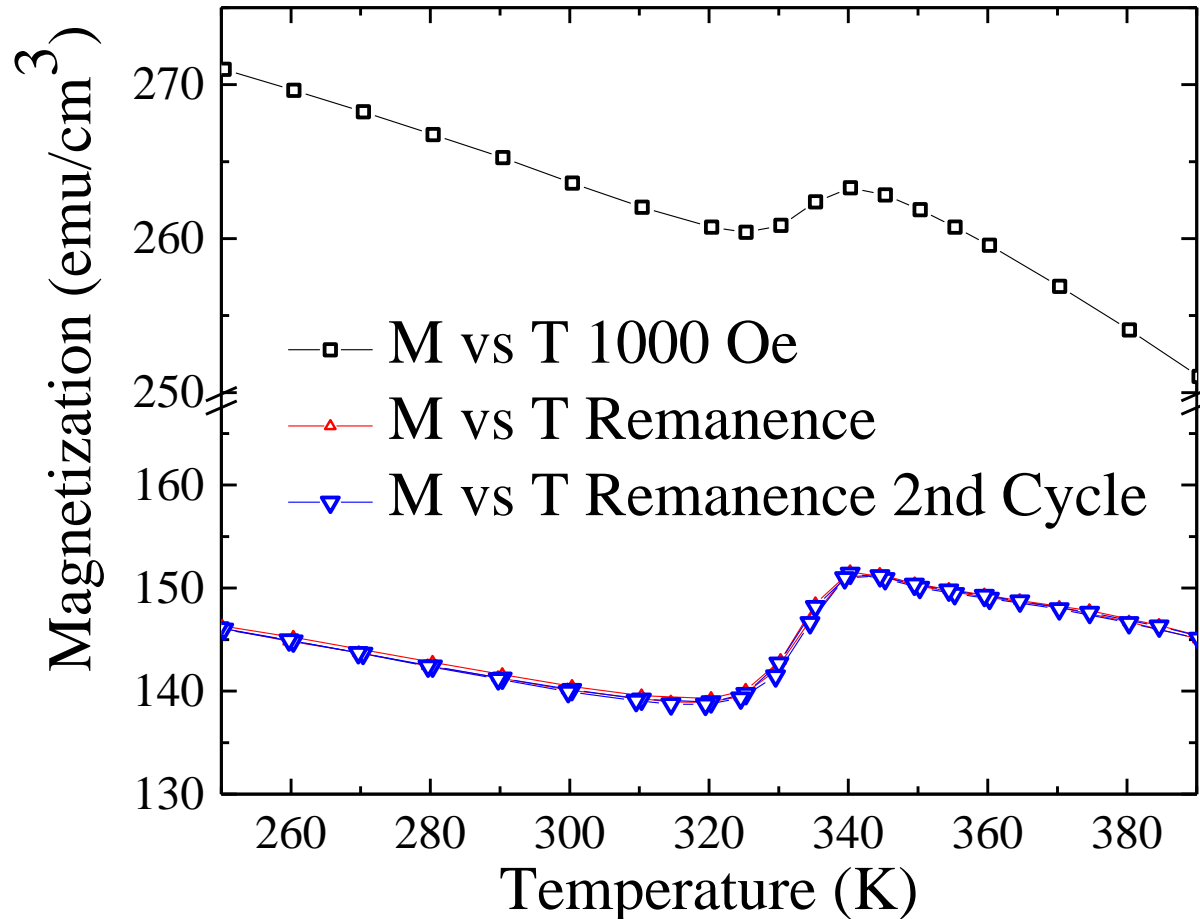

**Magnetic Domain Dynamics**

# Stress Anisotropy

100 nm VO<sub>2</sub> / 10 nm Ni

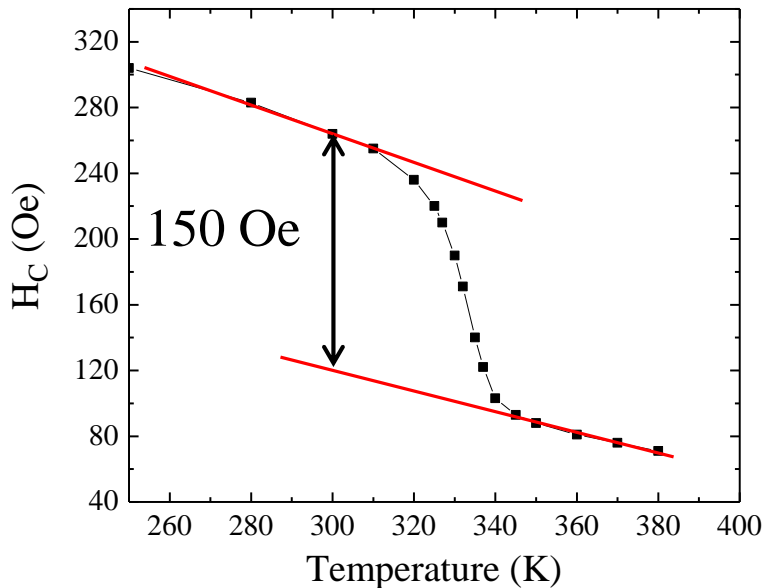

Stress Anisotropy Field

$$H_{K\sigma} = \frac{3\lambda\sigma}{M_S}$$

$$M_S = 470 \text{ emu/cm}^3$$

$$\lambda = -34 \times 10^{-6} \text{ Polycrystalline Ni}$$

➔  $\sigma \sim 59 \text{ MPa}$


Stress Measured in VO<sub>2</sub> Films  $\sigma \sim 400 \text{ MPa}$

B. Viswanath *et al.*, Scr. Mater. **64**, 490 (2011)

# Tailoring the Effect

- Ni Deposited at 420 K  
→ VO<sub>2</sub> Rutile
- Ni Deposited at RT  
→ VO<sub>2</sub> Monoclinic


Reverse the Effect by  
Selecting the Deposition  
Temperatures, i.e. VO<sub>2</sub>  
Structures

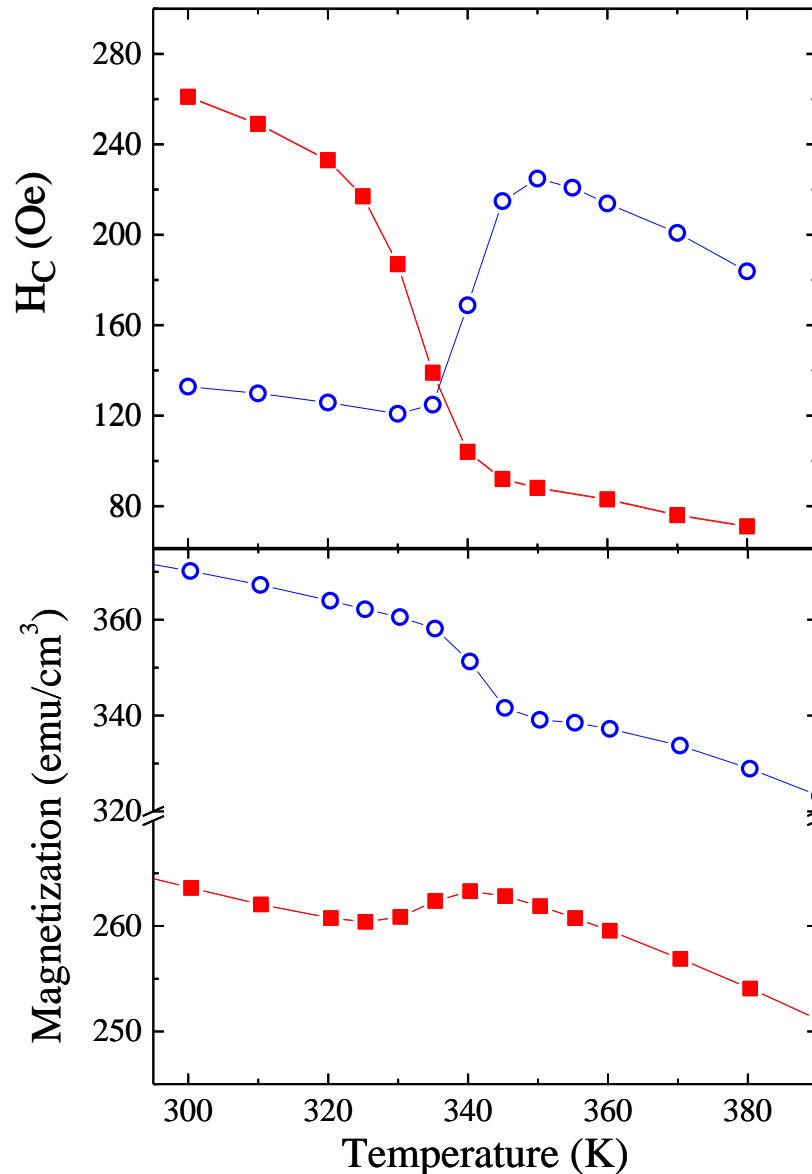

# Phase Transition in $V_2O_3$


MIT

SPT

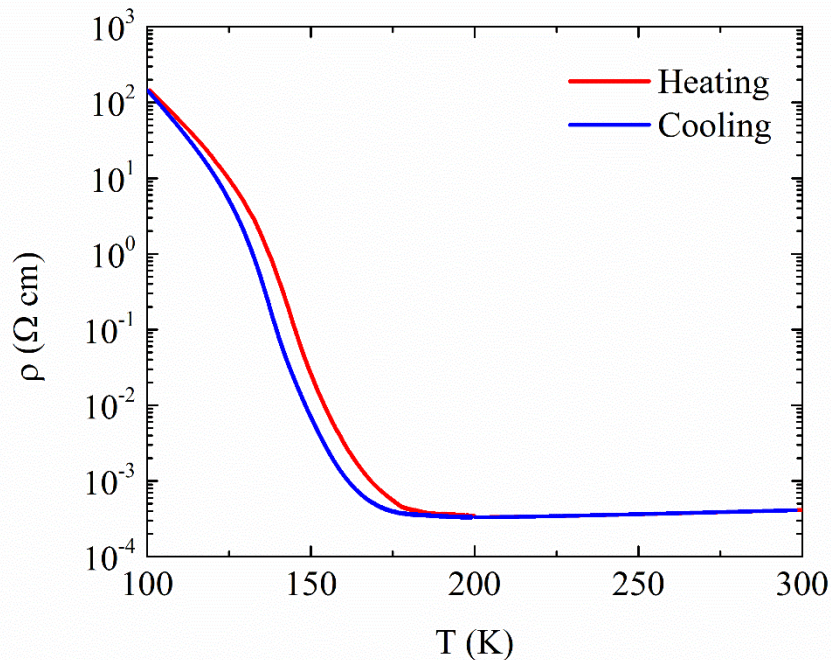

$$T_C = 150 - 165 \text{ K}$$

High-T Rhombohedral Low-T Monoclinic

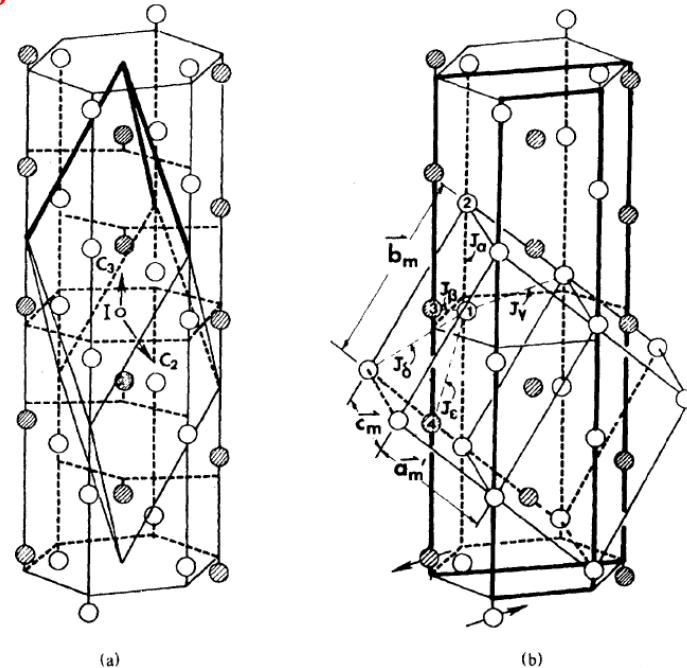

R. E. Word *et al.*, Phys. Rev. B **23**, 3533 (1981)



~ 1 % Lattice Distortion

~ 1 % Volume Change

# V<sub>2</sub>O<sub>3</sub> / FM: Generalization

100 nm V<sub>2</sub>O<sub>3</sub> { 10 nm Ni  
10 nm Co

100 nm V<sub>2</sub>O<sub>3</sub> { 10 nm Ni  
10 nm Fe

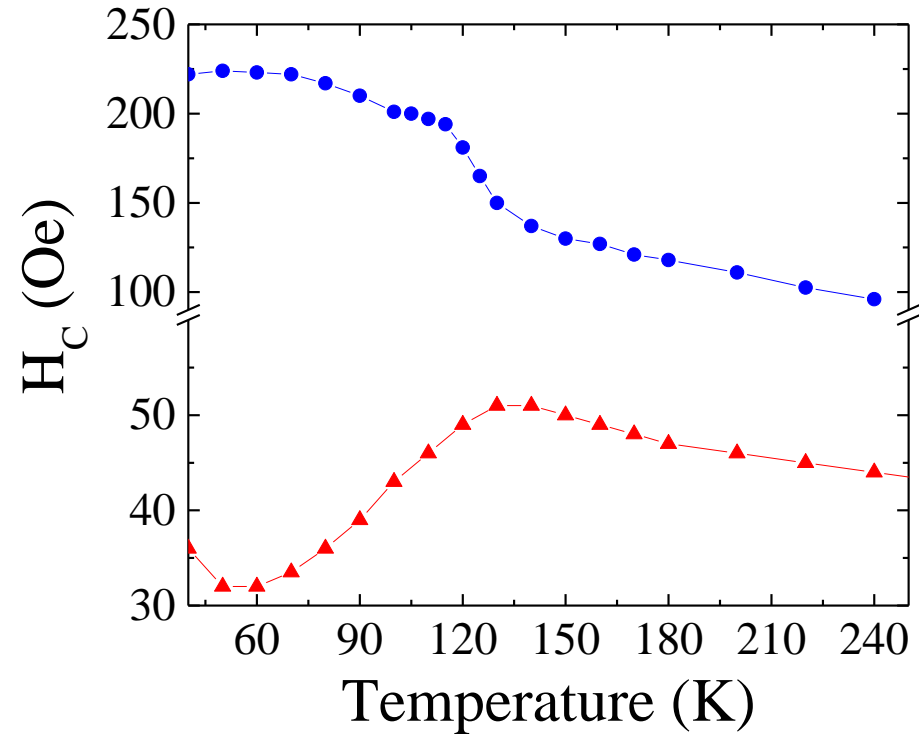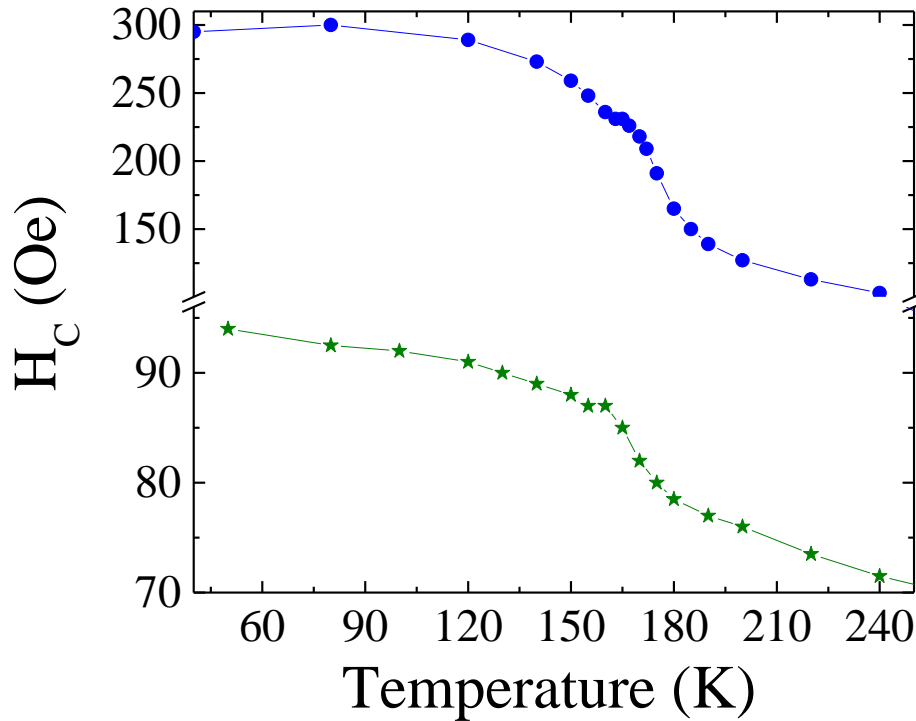

- Fe & Co Smaller Effect ← Smaller  $\frac{\lambda}{M_S}$
- Fe Inverse Effect ←  $\lambda_{Fe} > 0$

$$H_{K\sigma} = \frac{3\lambda\sigma}{M_S}$$



# Control of Magnetism with VO<sub>x</sub>/FM

- Control **Coercivity** & **Magnetization** with **SPT** of VO<sub>x</sub>
- Interface Effect – **Reduces with Increasing FM Thickness**
- Tuning with Stress – **Choose Deposition Temperatures**
- Tuning with FM – **Choose  $\lambda$  &  $M_s$**

J. de la Venta, S. Wang, J. G. Ramírez, and Ivan K. Schuller, Appl. Phys. Lett. **102**, 122404 (2013)

T. Saerbeck, J. de la Venta, S. Wang, J. G. Ramirez, M. Erekhinsky, I. Valmianski, I. K. Schuller, J. Mater. Res., Invited Review (2014)

I. K. Schuller, J. de la Venta, S. Wang, J. G. Ramirez, M. Erekhinsky, and A. Sharoni. Magnetic and Electrical Control of Engineered Materials. United States Patent 61/915,715, Issued December 13, 2013

# Outline

- *Introduction*

- Review Control of Magnetism
- Phase Transition in Vanadium Oxide ( $\text{VO}_x$ )

- *Control of Magnetism with  $\text{VO}_x/\text{FM}$*


- Tuning with Magnetostrictive Effect

- *Coercivity Enhancement in  $\text{V}_2\text{O}_3/\text{Ni}$*

- Competing Length Scale on Nanoscale



- *Conclusions*

# V<sub>2</sub>O<sub>3</sub>/Ni

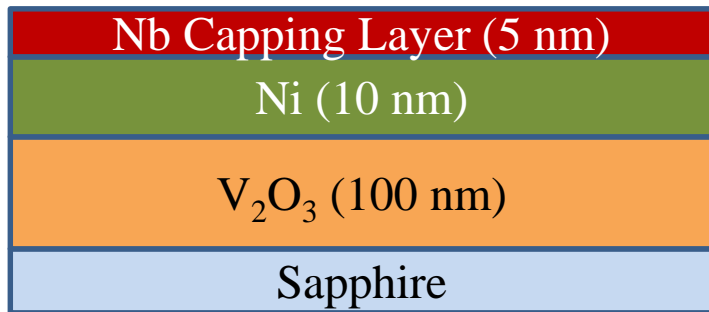


**Peak at T<sub>C</sub> = 150 – 165 K!**

**Coercivity Enhancement**

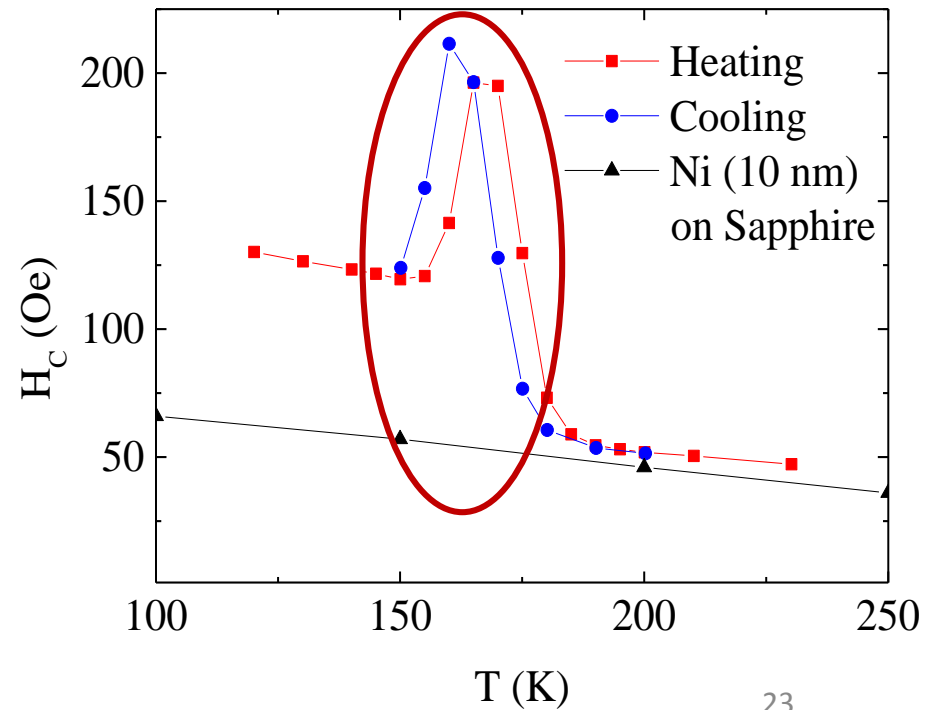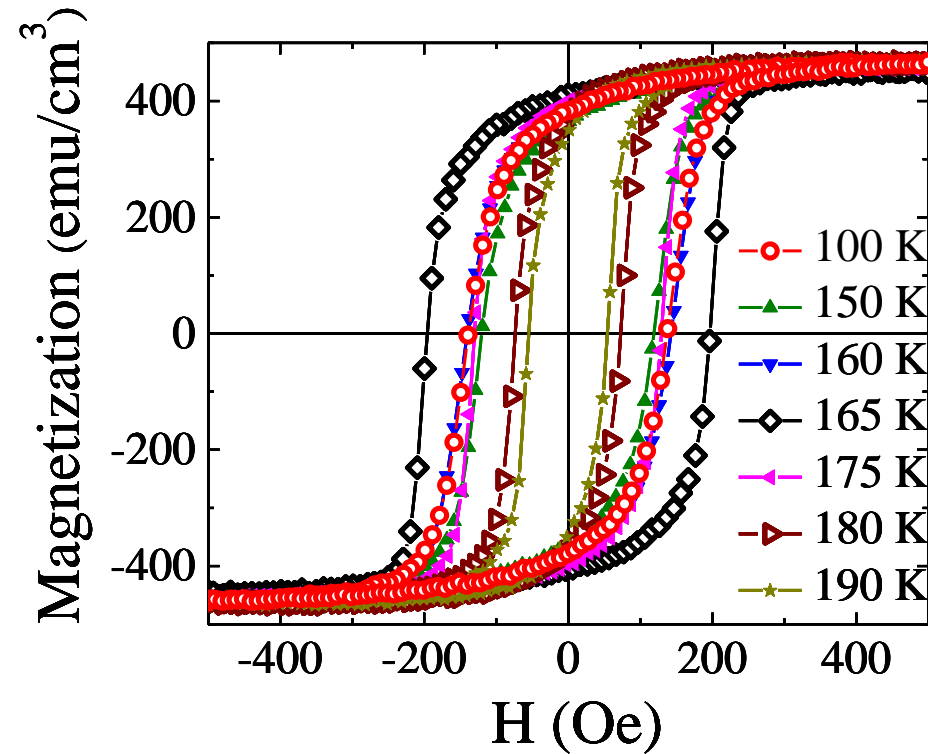

# Coercivity Enhancement

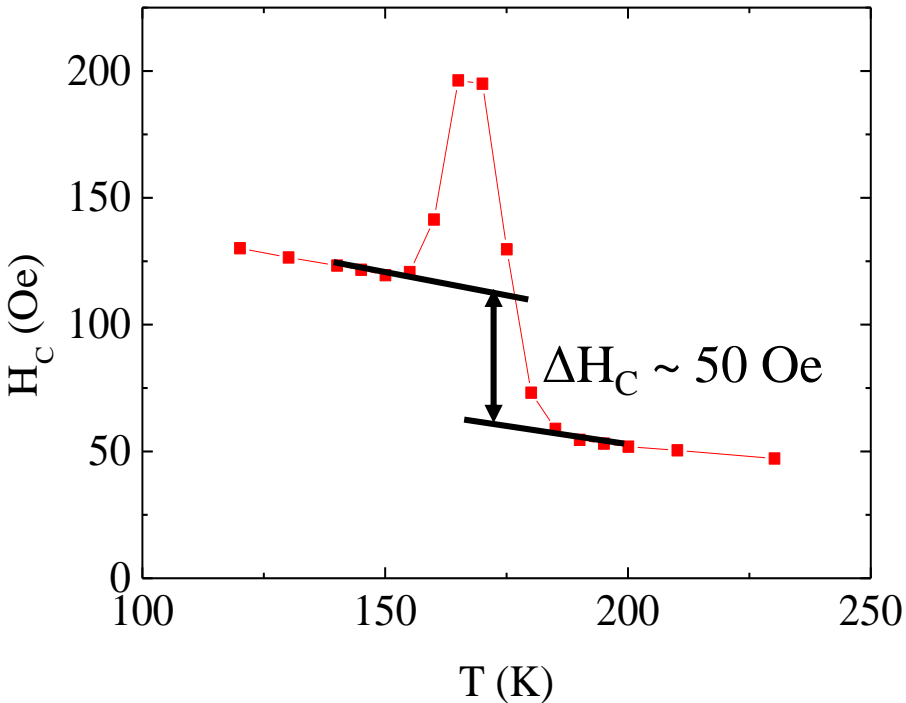

Structural Phase Transition in  $V_2O_3$



Stress in Ni  $\sim$  10's of MPa




Stress Anisotropy Field  $\sim$  50 Oe

J. de la Venta, S. Wang, J. G. Ramirez, and I. K. Schuller, Appl. Phys. Lett. **102**, 122404 (2013)

# Coercivity Enhancement

What Reaches Maximum at  $T = 165$  K in  $V_2O_3$ ?

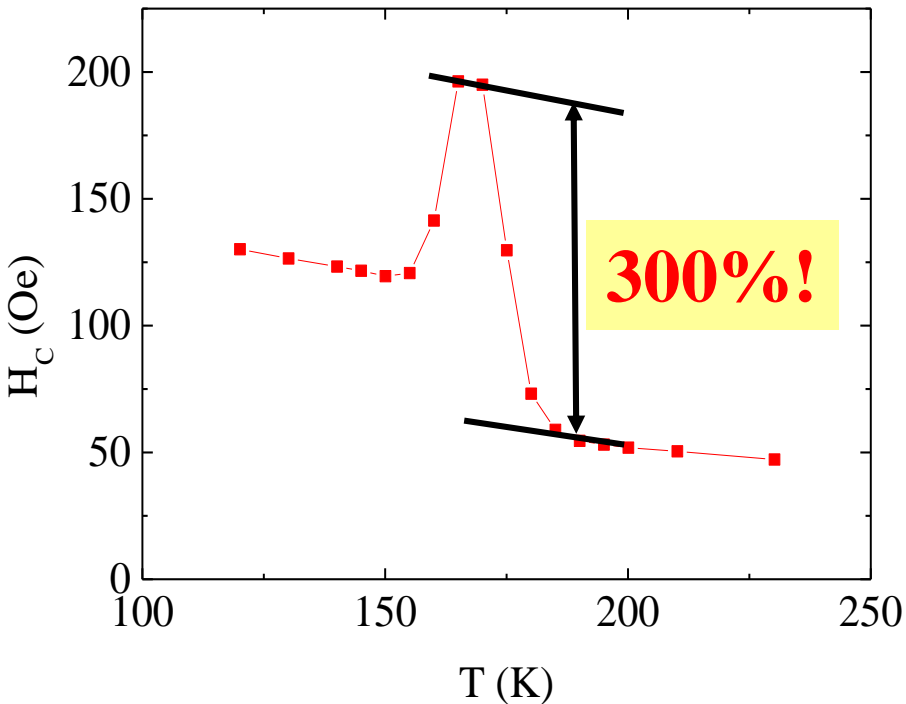

$H_C$  Reaches Maximum at  
 $T = 165$  K



Phase Coexistence in  $V_2O_3$




Single Phase Domain  
 $\lambda_{V_2O_3} \leq 100$  nm

A. S. McLeod *et al.*, J49.00011, Cryogenic Infrared Nano-Imaging of the Metal-Insulator Transition in  $V_2O_3$ , APS March Meeting, 2014

# Competing Length Scales

Surface Morphology

**Terraces**

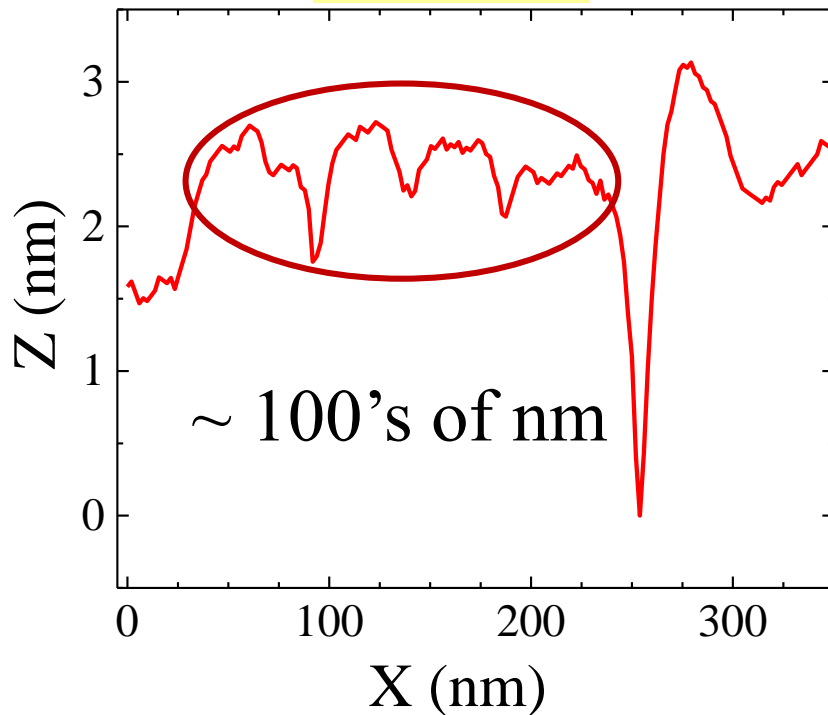

**Magnetic Domain  $d_{\text{Ni}} > 100$  nm**

**Single Phase Domain  $\lambda_{\text{V}_2\text{O}_3} \leq 100$  nm**

$$d_{\text{Ni}} > \lambda_{\text{V}_2\text{O}_3}$$



**Phase Coexistence of  $\text{V}_2\text{O}_3$**



**T-dependent Disorder**




**Enhanced Coercivity**




# Micromagnetic Simulation

Ni

$V_2O_3: \lambda_{V_2O_3} = 100 \text{ nm}$   
 $T = 165 \text{ K}$

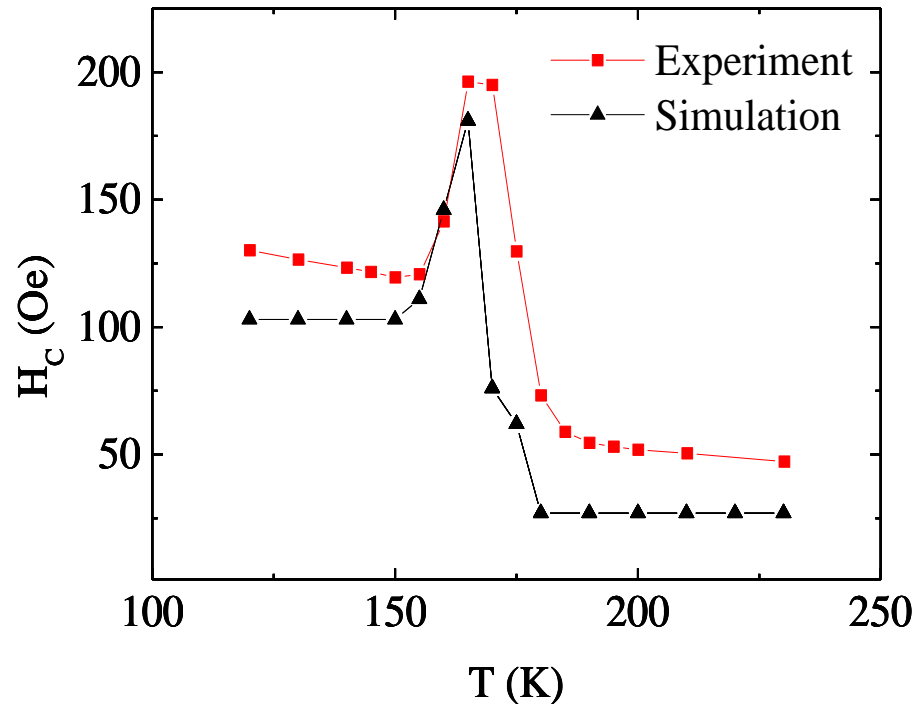

1  $\mu\text{m}^2$

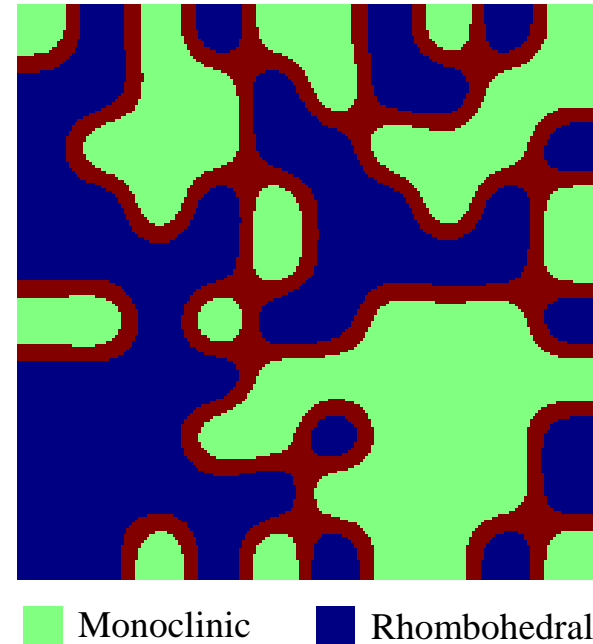

$K_{\text{Stress}} = 1 \times 10^4 \text{ J/m}^3$     $K_{\text{Pin}} = 4 \times 10^4 \text{ J/m}^3$

**25 – 30 nm Boundary**

OOMMF, NIST

Gaussian Distribution of  $T_C$

$T_C(\text{Mean}) = 165 \text{ K}$

# Magnetization Reversal



1  $\mu\text{m}^2$

165 K



Before  $H_C$

H  $\longleftrightarrow$

After  $H_C$

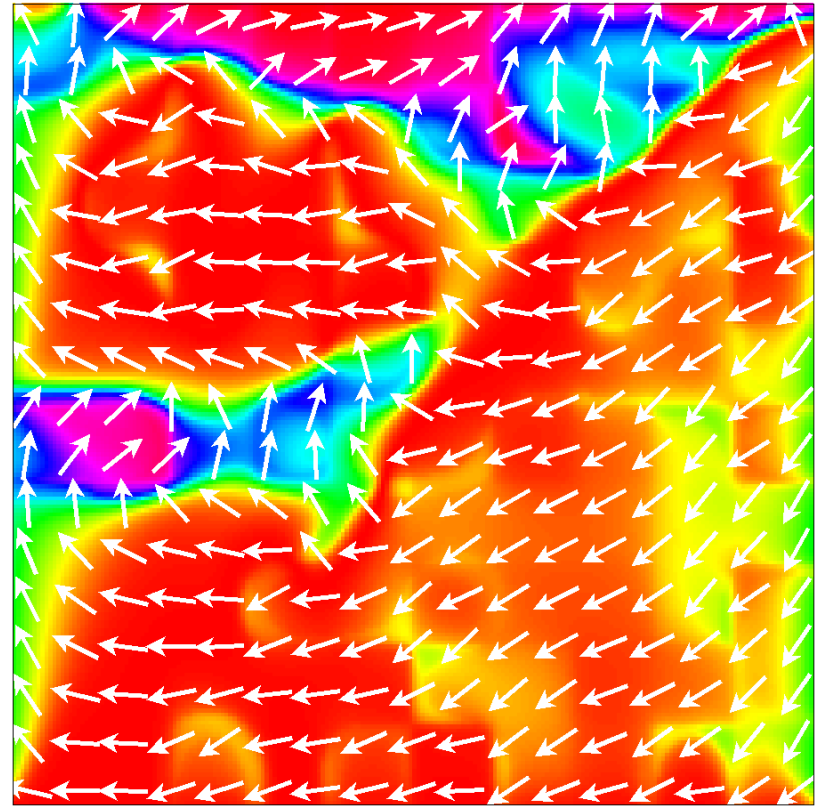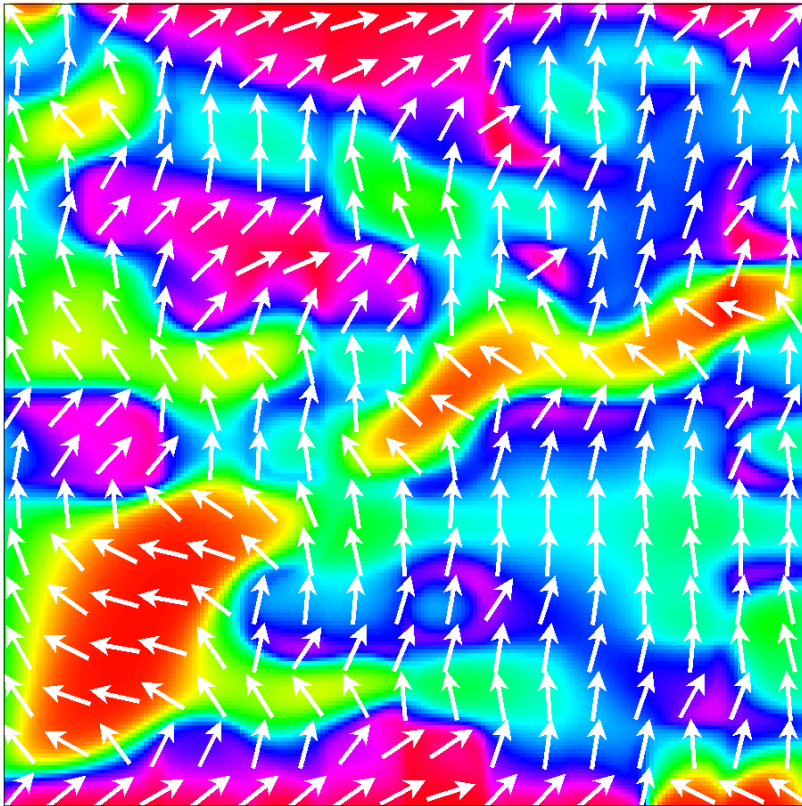

# Microstructure Comparison

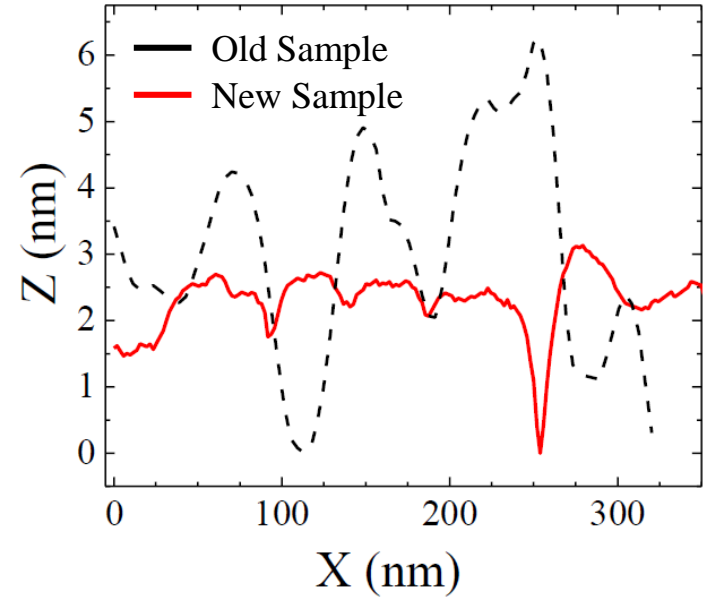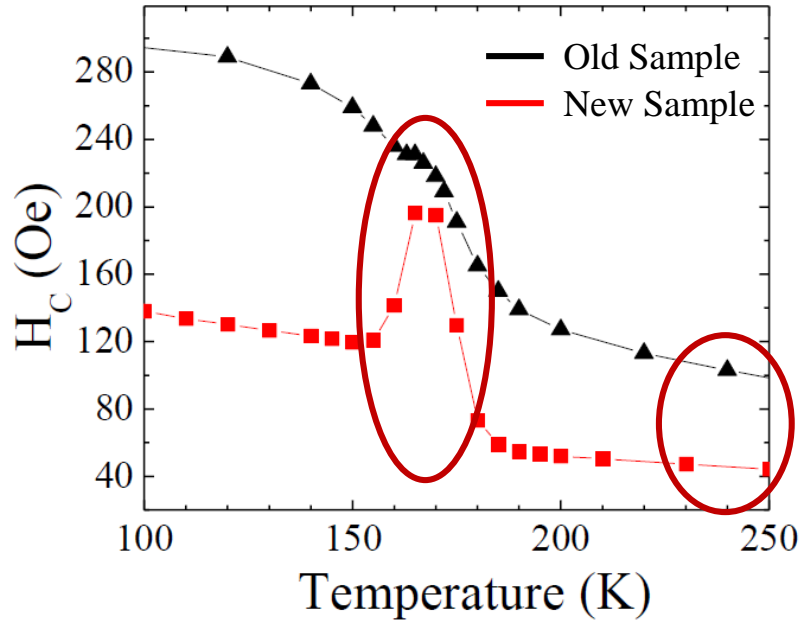

New Sample: 100's of nm Terraces (< 1 nm)

Old Sample: Higher Roughness (> 3 nm)



$$d_{\text{Ni}} > 100 \text{ nm}$$



**$d_{\text{Ni}} > \lambda_{\text{V}_2\text{O}_3}$ , Enhancement**



$$d_{\text{Ni}} \sim 50 - 100 \text{ nm}$$



**$d_{\text{Ni}} \approx \lambda_{\text{V}_2\text{O}_3}$ , No Enhancement**

# Coercivity Enhancement in $V_2O_3/Ni$

- Magnetic Measurement – **Enhanced Coercivity** in  $V_2O_3/Ni$
- Microstructure – **Competing Length Scales ( $d_{Ni}$  vs.  $\lambda_{V_2O_3}$ )**
- Model – **Phase Coexistence** Induced Pinning
- Simulation – **Quantitatively Reproduce** Enhanced Coercivity

J. de la Venta, S. Wang, T. Saerbeck, J. G. Ram ́rez, I. Valmianski, and Ivan K. Schuller, Appl. Phys. Lett. **104**, 062410 (2014)

T. Saerbeck, J. de la Venta, S. Wang, J. G. Ramirez, M. Erekhinsky, I. Valmianski, I. K. Schuller, J. Mater. Res., Invited Review (2014)

# Summary

- First Order SPT – **Large Stress within a Narrow Temperature Range**
- Multiple Driving Forces to Induce SPT – **Temperature, Voltage/Current, Light, Gating, Pressure and etc.**
- Multiple Tuning Parameters – **Different FMs & Deposition Conditions**
- Competing Length Scales – **Disorder due to Nanoscale Inhomogeneity**

# Outlook

- Probe  $V_2O_3$  Domain – **Scanning Near-Field Optical Microscopy (SNOM)**
- Probe Magnetic Domain in Ni – **Neutron Scattering**
- Coercivity Enhancement with  $VO_2$  – **Smooth Surface** (TiO<sub>2</sub> or MgF<sub>2</sub> Substrate)
- Dynamics (FMR) – **Damping Divergence due to Nanoscale Disorder**

swang@physics.ucsd.edu

<http://www.linkedin.com/pub/siming-wang/42/935/595>